



Material Modelling of the Post-Peak Response of Reinforced Concrete at Elevated Temperatures

Carstensen, Josephine Voigt; Pankaj, P.; Jomaas, Grunde

Publication date:
2011

Document Version
Publisher's PDF, also known as Version of record

[Link back to DTU Orbit](#)

Citation (APA):
Carstensen, J. V., Pankaj, P., & Jomaas, G. (2011). *Material Modelling of the Post-Peak Response of Reinforced Concrete at Elevated Temperatures*. Poster session presented at 10th International Symposium on Fire Safety Science, Maryland, United States. <http://www.iafss.org/html/Maryland/marylandhome.htm>

General rights

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal

If you believe that this document breaches copyright please contact us providing details, and we will remove access to the work immediately and investigate your claim.

MATERIAL MODELLING OF THE POST-PEAK RESPONSE OF REINFORCED CONCRETE AT ELEVATED TEMPERATURES

J.V. Carstensen^a, P. Pankaj^b and G. Jomaas^a

^a Department of Civil Engineering at the Technical University of Denmark (DTU)

^b BRE Centre for Fire Safety Engineering at the University of Edinburgh

MOTIVATION


For FE-analysis of reinforced concrete at elevated temperatures the current material models yield convergence problems for different mesh sizes. For ambient conditions, it has been established that using a **fracture energy** based material model circumvents this issue. It is therefore relevant to extend these models to the elevated temperature conditions.

FRACTURE ENERGY


The fracture energy is a material invariant that corresponds to the area beneath the stress-plastic displacement (or cracking) diagram.

TENSION STIFFENING

The uncracked part of the concrete still contributes to the strength after cracking is initiated.

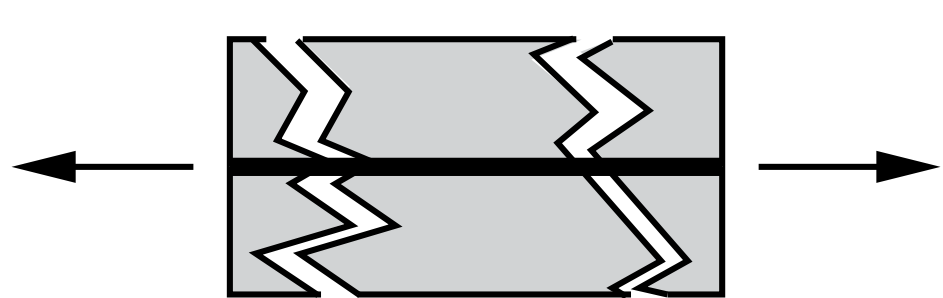


This can be modelled based on the fracture energy by an interaction stress contribution as suggested by Cervenka et al. and Feenstra and de Borst.

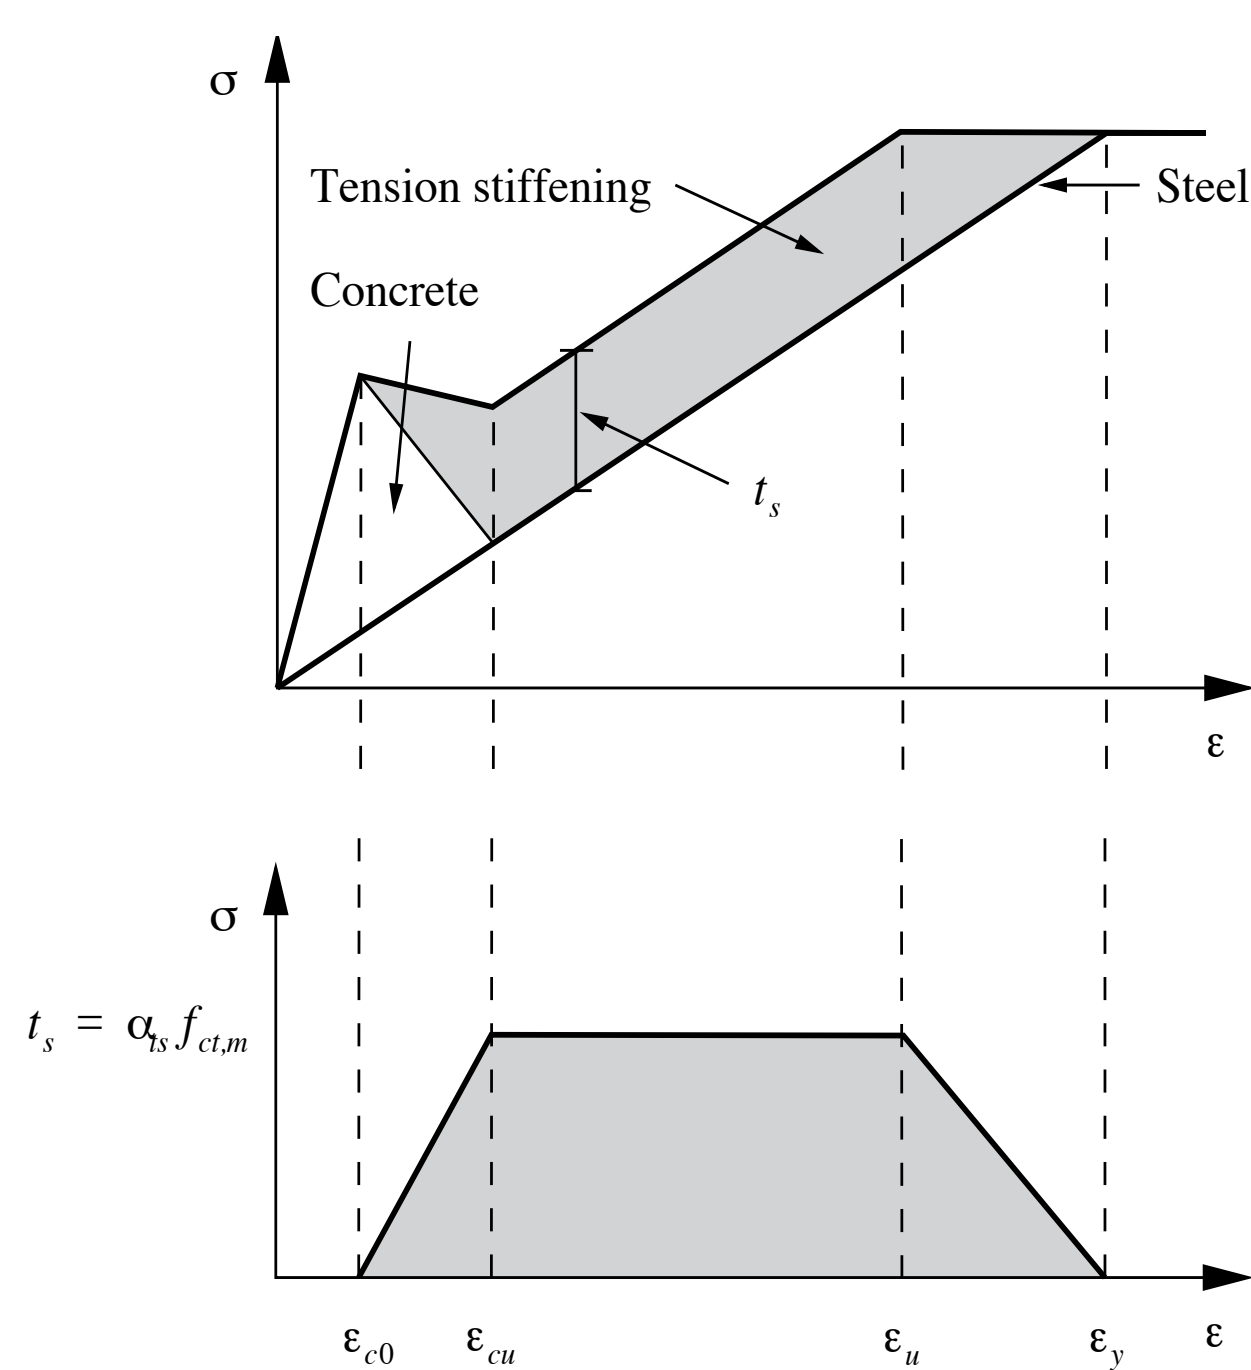

Problems in the Ambient Condition


A validity range for the element size and a minimum reinforcement ratio is formulated.

Compressive behaviour

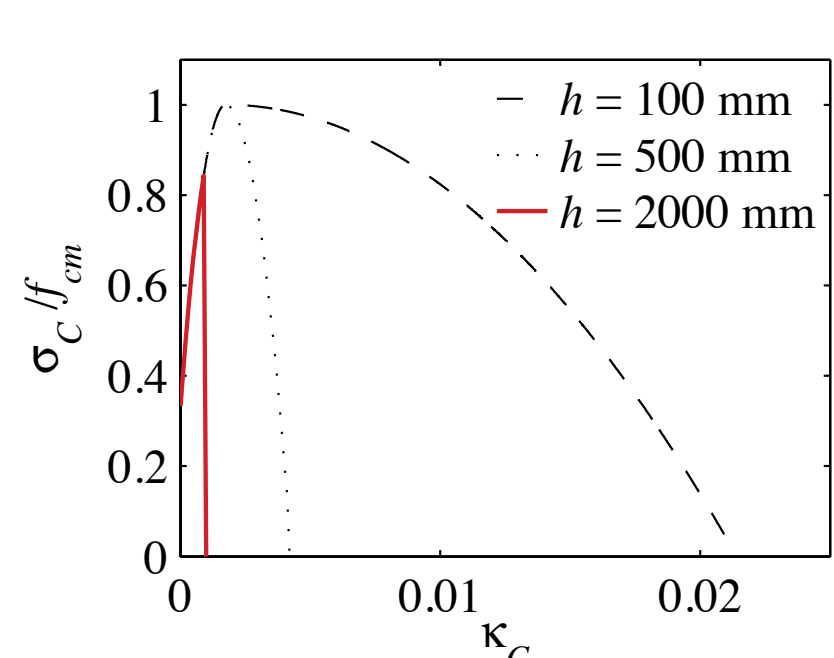


Element is too large


Tensile behaviour; combined concrete and interaction stress contribution

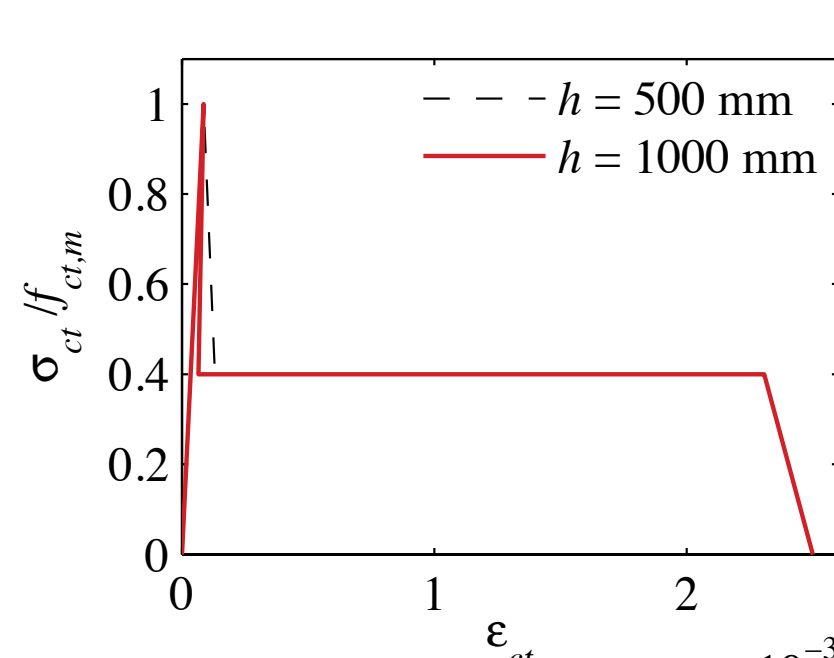

Element is too large

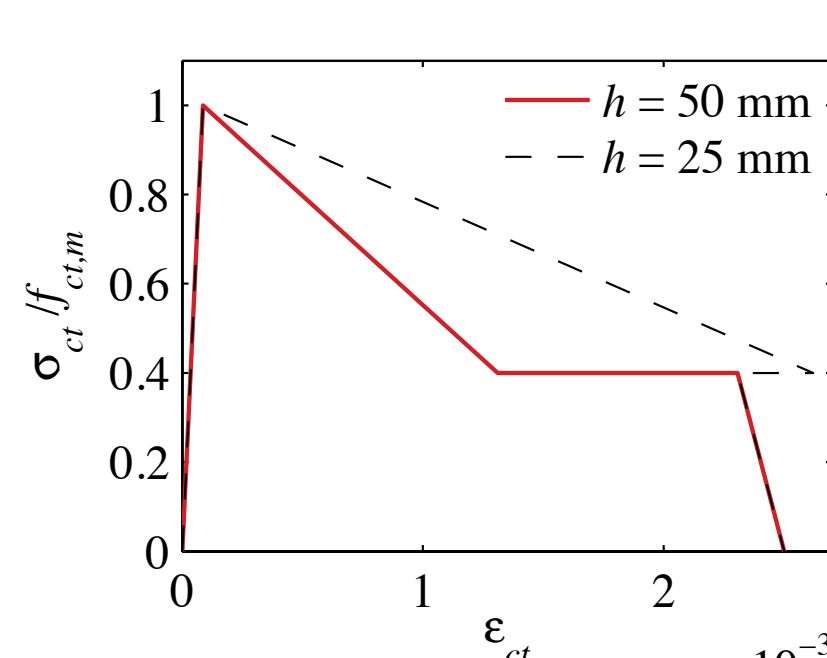

Element is too small

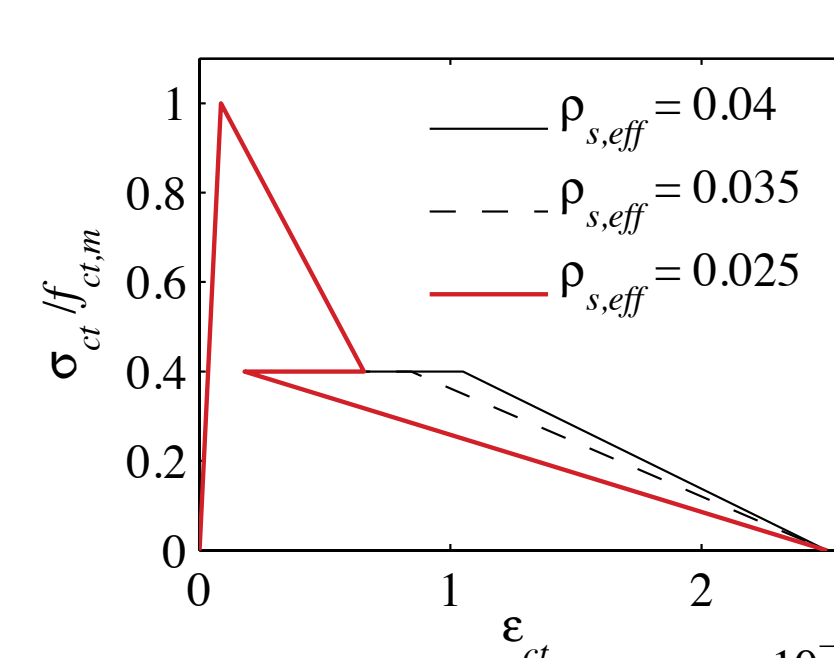

The reinforcement ratio is too small

EVOLUTION OF FRACTURE ENERGY WITH TEMPERATURE

The inherent fracture energies are found as function of temperature for the existing elevated temperature behaviour models for concrete.

Tensile Fracture Energy

Based on the model by Terro, G_{fT} follows the decay of tensile strength;

$$G_{fT} = \xi(T) \cdot G_f$$


Compressive Fracture Energy

G_{cT} is found for the models by;

— — — Lie and Lin
— — — Anderberg and Thelandersson

And the models including the effect of the load induced thermal strains (LITS) by;


..... Li and Purkiss
— — — Eurocode 2

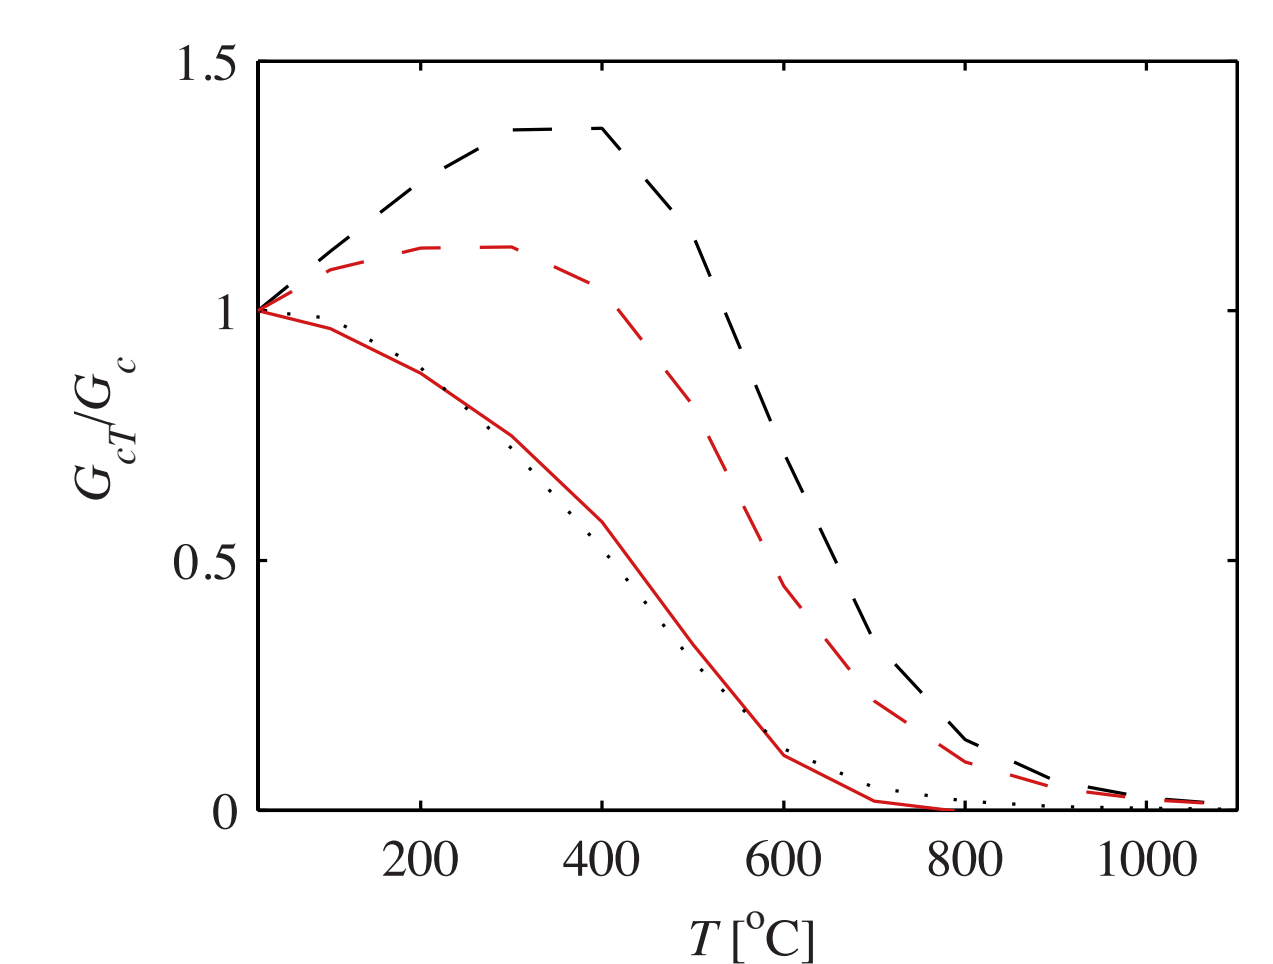


EXAMPLE

REINFORCED CONCRETE SLAB

Concrete grade C30 and steel Grade 500 and G_{cT} as is computed as inherent in Eurocode 2.

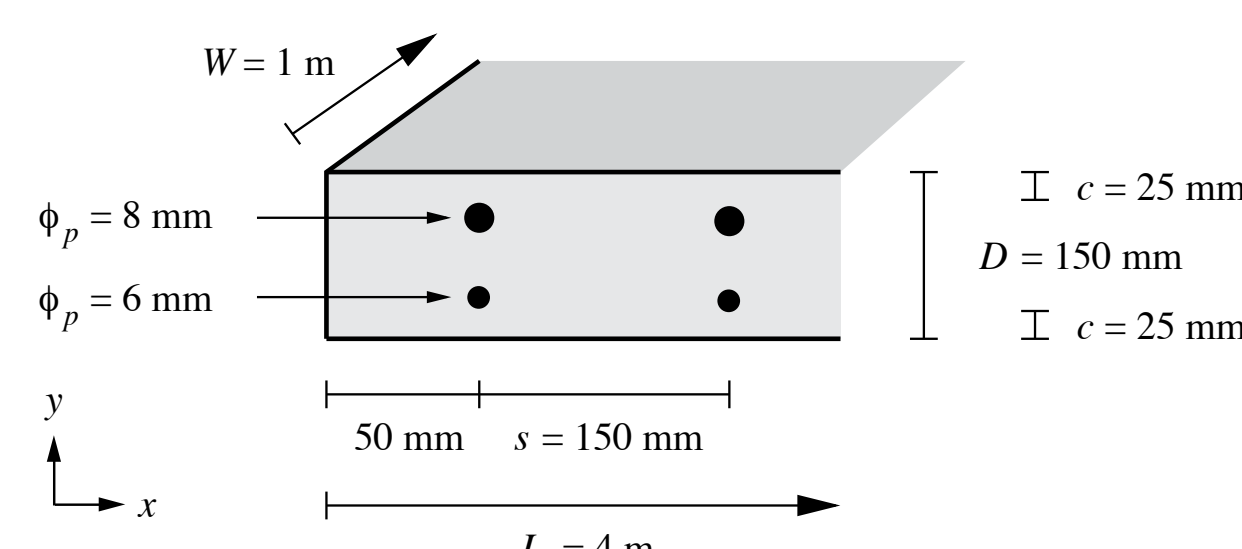

The validity range for the element size:

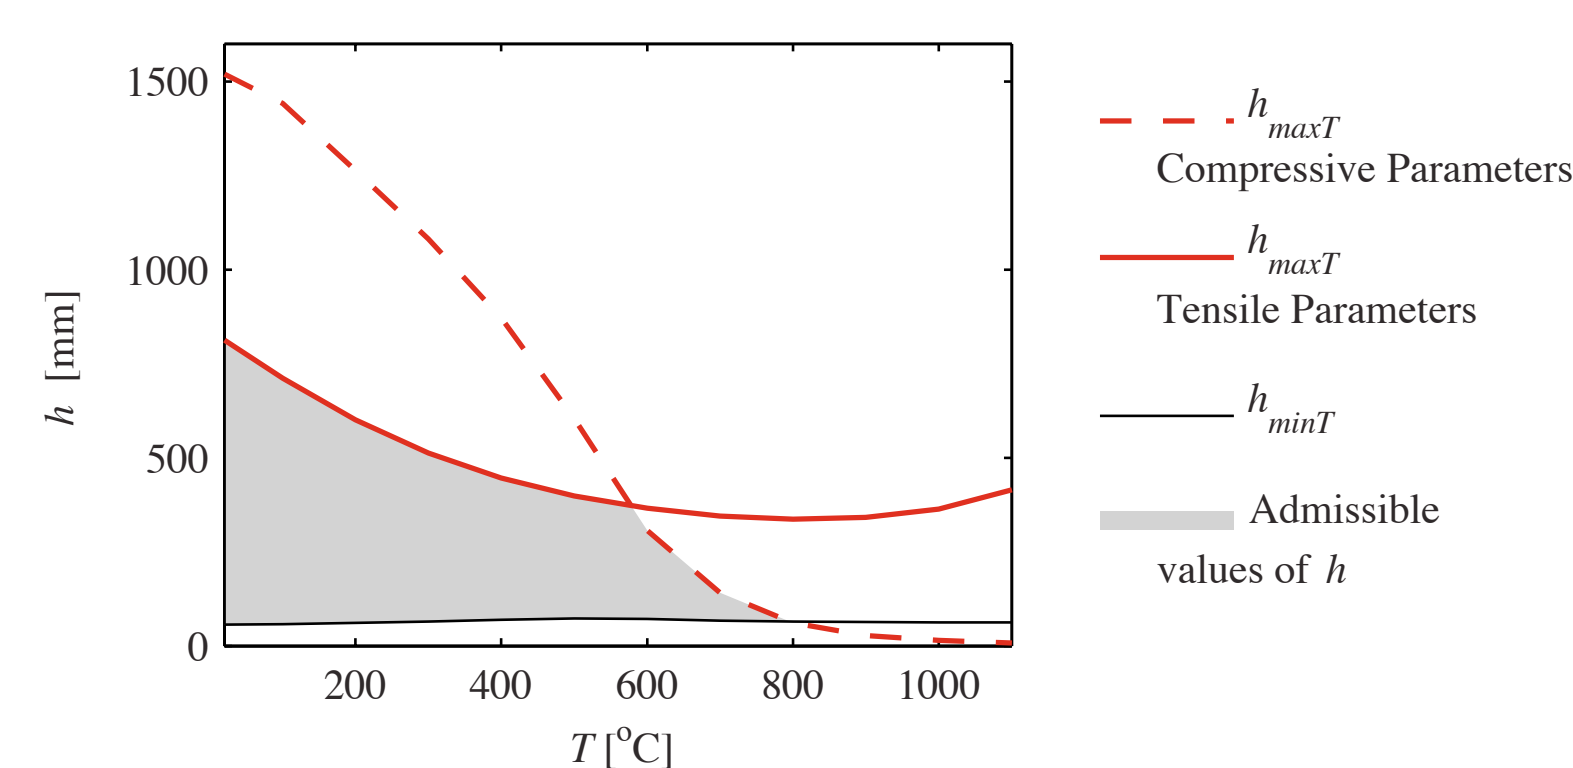

$T_{max} = 715$ °C and the hence

$$72.5 \text{ mm} < h < 129.6 \text{ mm}$$

The level of reinforcement is found to be sufficient.

CONCLUSION

- G_{fT} follows the decay of material strength.
- There is a significant spread in the existing compressive post-peak behaviours.
- The LITS does not appear to influence G_{cT} .
- For the considered example, analysis above 800 °C will not converge.

REFERENCES

- Cervenka et al., *Computer Aided Analysis and Design of Concrete Structures*, Pineridge Press, 1-21 (1990)
- Feenstra and de Borst, *Journal of Engineering Mechanics* 121: 587-595 (1995)
- Anderberg and Thelandersson, Lund (1976)
- Lie and Lin, *Fire Safety: Science and Engineering* 882: 176-205 (1985)
- Li and Purkiss, *Fire Safety Journal* 40(7): 669-686 (2005)
- Eurocode 2 - Part 1-2, CEN (2004)
- Terro, *ACI Structural Journal* 95(2): 183-193 (1998)